



Ceramic Restorations Based on Zirconium Dioxide for Orthopedic Dentistry

**Alina Anatolyevna Muzayeva^a, Abulmuslim Magomedovich Nuraliev^b,
Saida Astanovna Temirova^a, Elena Anatolyevna Muzaeva^b,
Turpal-Ali Arsanovich Adaev^c, Zarina Vadimovna Kudzieva^a,
Muslim Temirkhanovich Chantiev^a, Zelimkhan Uvaysovich Akhmetov^{a*}
and Lyana Khachimovna Bizhoeva^a**

^a *North Ossetian State University Named After K. L. Khetagurov, Vladikavkaz, Republic of North Ossetia-Alania, Russia.*

^b *Moscow State University of Medicine and Dentistry Named After A. I. Evdokimov, Moscow, Russia.*

^c *Stavropol State Medical University, Stavropol, Russia.*

Authors' contributions

This work was carried out in collaboration among all authors. All authors read and approved the final manuscript.

Article Information

DOI: 10.9734/JPRI/2021/v33i55B33862

Open Peer Review History:

This journal follows the Advanced Open Peer Review policy. Identity of the Reviewers, Editor(s) and additional Reviewers, peer review comments, different versions of the manuscript, comments of the editors, etc are available here: <https://www.sdiarticle5.com/review-history/78712>

Original Research Article

**Received 06 October 2021
Accepted 12 December 2021
Published 13 December 2021**

ABSTRACT

Currently, ceramics based on solid solutions of zirconium dioxide tetragonal structure are common biomedical materials. In commercially common ceramics of orthopedic dentistry based on zirconium dioxide, the stabilization of the tetragonal shape is achieved by the introduction of yttrium or cerium cations. As a result of this scientific work, a ceramic material based on nanopowders of a system of zirconium dioxide and ytterbium oxide with high strength parameters has been developed. The results of the conducted research allow us to recommend the new Yb-TZP ceramics as an alternative to Y-TZP ceramic materials for restorations in orthopedic dentistry.

Keywords: *Zirconium dioxide; ytterbium oxide; Yb-TZP ceramics; Y-TZP ceramics; restoration in orthopedic dentistry.*

1. INTRODUCTION

Currently, ceramics based on solid solutions of zirconium dioxide tetragonal structure (TZP) are common biomedical materials. These ceramics have bioinertness, which is combined with good biocompatibility and low invasiveness, as well as high strength characteristics [1-5].

According to scientific research, ceramics based on zirconium dioxide does not cause allergies or signs of incompatibility in the oral cavity [6]. In addition, zirconium dioxide is biocompatible with the mucous membrane and tissues of the oral cavity [7]. High functional stability and corrosion resistance, as well as impeccable aesthetic and mechanical characteristics make up the undeniable advantages of the material [8]. Zirconium dioxide does not participate in galvanic processes and passes X-rays [9]. The use of this material eliminates the problem of temperature sensitivity due to thermal insulation and low thermal conductivity [10]. Three groups of ceramics are used in dentistry: polycrystalline, infiltration and glass ceramics. Glass ceramics and infiltration ceramics are multiphase materials containing crystalline components in addition to the amorphous phase of glass. Zirconium oxide is the only type of polycrystalline ceramics, and in its properties it surpasses other types of ceramics, since it contains very little glass and, therefore, has a high long-term strength [11].

In commercially common ceramics of orthopedic dentistry based on zirconium dioxide, the stabilization of the tetragonal shape is achieved by the introduction of yttrium or cerium cations. It is known that the strength properties of PZT ceramics containing Y^{+3} cations are subject to gradual degradation (Low Temperature Degradation) during prolonged exposure to the body environment, which leads to revision operations. The substitution of the stabilizing cation Y^{+3} for Ce^{+4} favors an increase in the stability of strength properties in the biological medium [12,13]. However, such ceramics do not meet the requirements of aesthetic orthopedic dentistry for the color rendering of the material.

The aim of this work was to develop a ceramic material based on nanopowders of a system of zirconium dioxide and ytterbium oxide with high strength parameters, stable during prolonged stay in the biological environment, and having a color rendering close to natural teeth for restorations in orthopedic dentistry.

2. MATERIALS AND METHODS

The synthesis of precursors of powders of the ZrO_2 - Yb_2O_3 system containing 95-97% ZrO_2 (Yb-TZP) was carried out by the hydrolysis sol-gel method using 1 M solutions of $ZrOCl_2$; $Yb(NO_3)_3$ salts according to the procedure described in [14,15]. The initial powders were obtained after heat treatment of gel-like precipitates (hydrogels) at final temperatures of 450°, 750° and 950°C.

Blanks from synthesized powders - disks \square 20 mm and prisms 32x7x3 mm - were compacted by semi-dry pressing [16].

Sintering was carried out in electric furnaces in an air environment at a final temperature of 1500°C.

The relative density and porosity of sintered ceramic samples were determined by the method of hydrostatic weighing (Archimedes). The method of low-temperature adsorption (adsorption-structural analyzer "TriStar -3000") was used to measure the specific surface of powders [17].

The bending strength was determined by the three-point bending method on the Instron 5581 universal testing machine. The speed of movement of the traverse of the test machine is - 0.5 mm/min [18].

In order to assess the stability of the properties of Yb-PZT ceramics during prolonged exposure to a living organism, a method of accelerated aging due to hydrothermal treatment of ceramic samples according to ISO 13356-2008 was used. The accelerated aging test was performed at a temperature of 134°C and a pressure of 2 bar.

Qualitative analysis of the phase composition of ceramics before and after hydrothermal treatment was carried out on an Ultima IV diffractometer (X-ray radiation, nickel filter), angle interval $2\theta=20-70^\circ$ [19]. Phase identification was performed using the PDF2 radiometric data bank.

The evaluation of the color characteristics of ceramic samples was carried out on the Spectron-M2 apparatus. In the CIE color system (CIE $L^*A^*B^*$), three parameters L^* , A^* and B^* are used to determine the color. The value of L^* is consistent with the idea of the lightness of the object. Parameters A^* and B^* allow you to

express the color of the object and its saturation. A sample of barium sulfate was used as a reference. The value ΔE characterizes the deviation from the standard.

3. RESULTS AND DISCUSSION

The degree of crystallization of the synthesized powders increases in proportion to the increase in the temperature of the heat treatment of gel-like precipitation from 450°C to 950°C. The main phase of the powders is represented by a solid solution based on zirconium dioxide, the

structure of which is being improved from pseudocubic to tetragonal, which is illustrated in Fig. 1, where fragments of diffractograms of powders obtained at temperatures of 450°, 750° and 950°C are presented.

Powders (Yb–TZP) obtained at a temperature of 950°C have a high dispersion, a specific surface area of at least 20 m²/g, which corresponds to the size of individual particles of no more than 50 nm. This fact is illustrated in Fig. 2, where an electronic snapshot of the powder is presented.

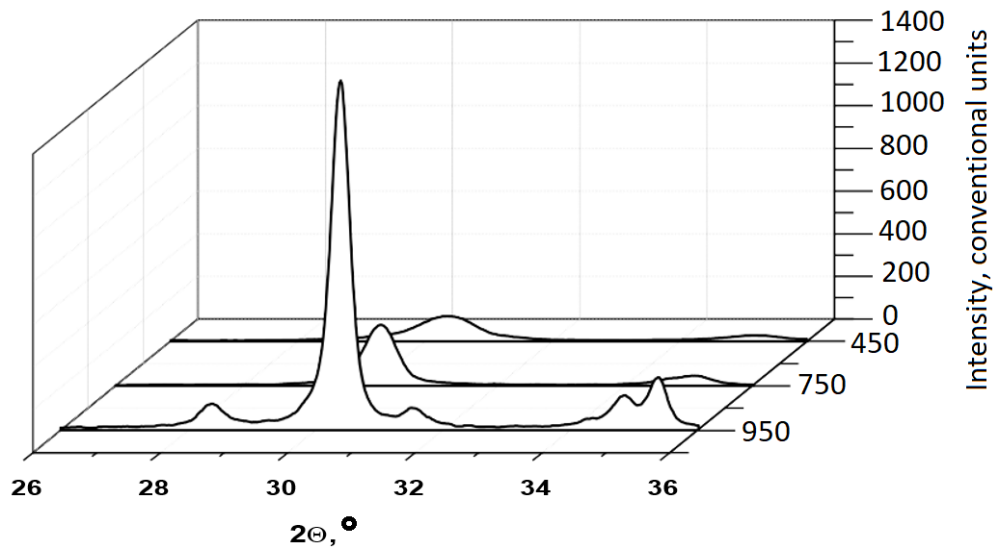


Fig. 1. Fragments of diffractograms of Yb–TZP powders

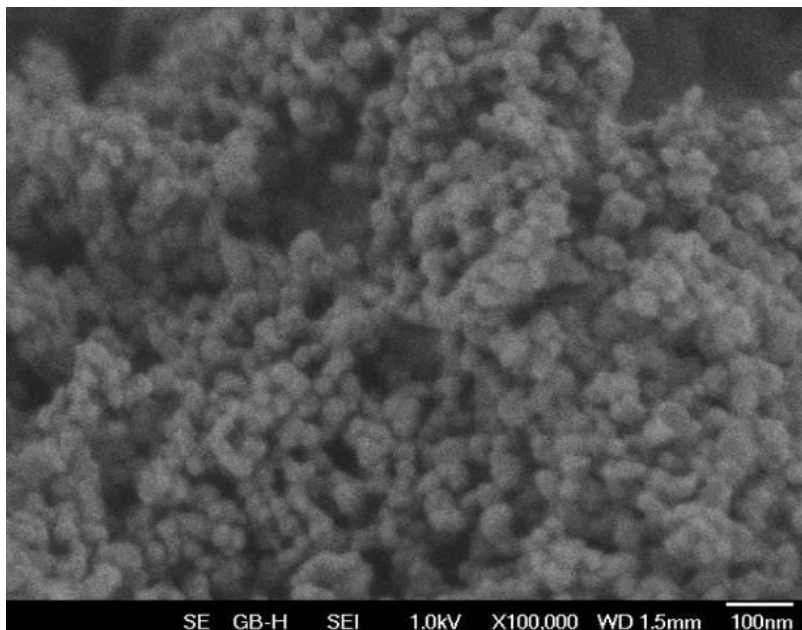


Fig. 2. Electronic micrography of powder

The high dispersion of the powders led to the achievement of a dense state of ceramic samples after sintering. At the final sintering temperature of 1500°C, the relative density of Yb-TZP samples reaches 99% of the theoretical density. The microstructure of Yb-TZP ceramics is dominated by grains ranging in size from 300 to 500 nm, which is confirmed by the electronic image of the ceramic surface shown in Fig. 3.

The effect of hydrothermal treatment on the phase composition of Y-TZP and Yb-TZP

ceramics was compared. It was found that two phases corresponding to solid solutions based on ZrO₂ tetragonal and monoclinic modifications are identified on the surface of the samples, as shown in Fig. 4.

It can be stated that as a result of hydrothermal treatment, a greater amount of M-ZrO₂ phase is formed in the phase composition of Y-TZP ceramics in comparison with Yb-TZP ceramics. This fact indicates a greater stability of the developed ceramics.

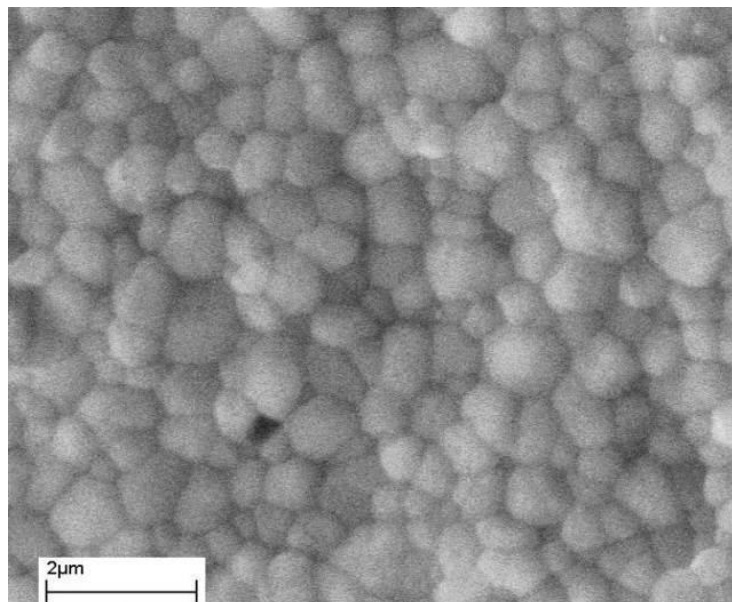


Fig. 3. Microstructure of sintered ceramics Yb-TZP

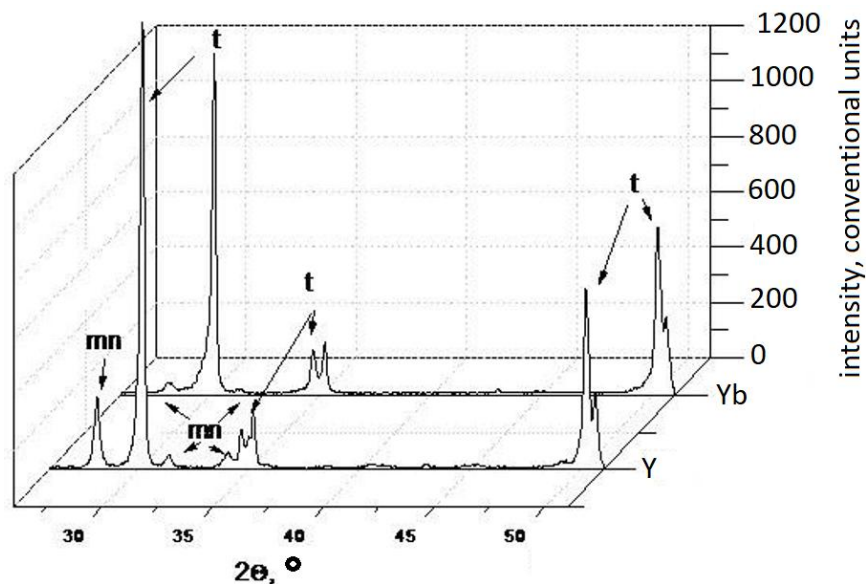


Fig. 4. Fragments of diffractograms of the surface of Y-TZP and Yb-TZP samples after exposure to hydrothermal treatment

Table 1. Average values of mechanical characteristics of Yb – PZT ceramics

Parameters	Strength, MPa		Crack resistance, GPa		Resistance to degradation of mechanical properties, MPa·m ^{1/2}	
	Original	Hydrothermal treatment	Original	Hydrothermal treatment	Original	Hydrothermal treatment
Values	900	900	9.0	9.2	12.0	12.0
∇	±50		±0,2		±0,4	

Table 2. Color characteristics of samples

No	Sample	A	B	L	∇E
1	The standard	0,012	0,086	100,046	0,00
2	Yb–TZP	-0,72	2,737	90,116	10,35
3	Ce–TZP	-1,029	14,175	84,695	20,98

The parameters of the strength characteristics of the developed Yb–PZT material before and after accelerated aging under the influence of hydrothermal treatment are presented in Table 1.

The developed material Yb–PZT complies with the requirements of the international standard ISO 13356-2008 for strength, crack resistance and resistance to degradation of mechanical properties in conditions of low-temperature aging.

The color characteristics of the samples of the previously developed ceramics Ce–TZP and Yb–TZP were determined, the results are presented in Table 2.

It was revealed that the developed ceramics Yb–TZP in terms of color characteristics is more close to the standard than ceramics Ce–TZP, respectively $\Delta E = 10$ and 21 units.

4. CONCLUSION

A ceramic material based on nanopowders of a system of zirconium dioxide and ytterbium oxide with high strength parameters has been developed.

The positive effect on the stability of the phase composition and strength properties of TZP ceramics under conditions of accelerated low-temperature aging of the replacement of the Y³⁺ cation stabilizing the tetragonal form of zirconium dioxide with the Yb³⁺ cation has been established.

The developed Yb–TZP ceramics are close to the standard in terms of color characteristics.

The results of the study allow us to recommend Yb–TZP ceramics as an alternative to Y–TZP ceramic materials for restorations in orthopedic dentistry. Preliminary economic calculation shows that the introduction of Yb-TZP ceramics is economically justified and will not be more expensive than using standard Y-TZP ceramic.

DISCLAIMER

The products used for this research are commonly and predominantly use products in our area of research and country. There is absolutely no conflict of interest between the authors and producers of the products because we do not intend to use these products as an avenue for any litigation but for the advancement of knowledge. Also, the research was not funded by the producing company rather it was funded by personal efforts of the authors.

CONSENT

It is not applicable.

ETHICAL APPROVAL

It is not applicable.

ACKNOWLEDGEMENT

The work was carried out using the Center for Collective Use of the North Caucasus Federal University

COMPETING INTERESTS

Authors have declared that no competing interests exist.

REFERENCES

- Gremillard L, Chevalier J, Martin L, Douillard T, Begand S, Hans K, Oberbach T. Sub-surface assessment of hydrothermal ageing in zirconia-containing femoral heads for hip joint applications. *Acta Biomater.* 2018 Mar 1;68:286-295. DOI: 10.1016/j.actbio.2017.12.021
- Chevalier, Jérôme, Gremillard, Laurent. *Ceramics for Medical Applications: A Picture for the Next 20 Years.* Journal of the European Ceramic Society. 2009;29:1245-1255. DOI: 10.1016/j.jeurceramsoc.2008.08.025
- Vallet-Regí M. Revisiting ceramics for medical applications. *Dalton Trans.* 2006 Nov 28;(44):5211-20. DOI: 10.1039/b610219k
- Dmitry Anatolyevich Domenyuk, Vladimir Alexandrovich Zelensky, Igor Vladimirovich Rzhepakovsky, Oksana Ivanovna Anfinogenova, Application of Laboratory and X-Ray Central Studies un Early Diagnostics of Metabolic Disturbances of Bone Tissue in Children with Autoimmune Diabetes Mellitus , *Entomol Appl Sci Lett.* 2018;5(4):1-12.
- Gautam C, Joyner J, Gautam A, Rao J, Vajtai R. Zirconia based dental ceramics: structure, mechanical properties, biocompatibility and applications. *Dalton Trans.* 2016 Dec 6;45(48):19194-19215. DOI: 10.1039/c6dt03484e
- Tosiriwatanapong T, Singhatanadgit W. Zirconia-Based Biomaterials for Hard Tissue Reconstruction, Bone and Tissue Regeneration Insights. 2018;9(12):1-9.
- Arena A, Prete F, Rambaldi E, Bignozzi MC, Monaco C, Di Fiore A, Chevalier J. Nanostructured Zirconia-Based Ceramics and Composites in Dentistry: A State-of-the-Art Review. *Nanomaterials (Basel).* 2019 Sep 29;9(10):1393. DOI: 10.3390/nano9101393
- Ji1 Y, Zhang XD, Wang XC, Che ZC, Yu XM, Yang HZ. Zirconia bioceramics as all-ceramics crowns material: A review, *Rev. Adv. Mater. Sci.* 2013;34(2):72-78.
- Best SM, Porter AE, Thian ES, Huang J. Bio- ceramics: Past, present and for the future, *Journal of the European Ceramic Society.* 2008;28 (7):1319-1327.
- Alsulami U, Alshihri A, Huraib W, Alzahrani T, Albakkar H. The Effect of Coefficient of Thermal Expansion Differences on Bond Strength of Ceramic-Zirconia Interface, *IntJ Dent Med Res.* 2015;6.
- Bicalho LA, Baptista CARP, Barboza MJR, Santos C, Souza RC. ZrO₂-Bioglass Dental Ceramics: Processing, structural and mechanics characterization, *Advances in Ceramics –Electric and Magnetic Ceramics, Bioceramics, Ceramics and Environment.* 2011;20:451-472.
- Ban S, Sato H, Suehiro Y, Nakanishi H, Nawa M. Biaxial flexure strength and low temperature degradation of Ce-TZP/Al₂O₃ nanocomposite and Y-TZP as dental restoratives. *J Biomed Mater Res B Appl Biomater.* 2008 Nov;87(2):492-8. DOI: 10.1002/jbm.b.31131
- Ban S, Sato H, Suehiro Ya, Nakanishi H, Nawa M. Biaxial flexure strength and low temperature degradation of Ce-TZP/Al₂O₃ Nanocomposite and Y-TZP as Dental Restoratives.
- Lunin L, Lunina M, Kravtsov, Alexander, Sysoev I, Blinov Andrey, Pashchenko A. Effect of the Ag Nanoparticle Concentration in TiO₂-Ag Functional Coatings on the Characteristics of GaInP/GaAs/Ge Photoconverters. *Semiconductors.* 2018;52:993-996. DOI: 10.1134/S1063782618080122.
- Lunin L, Lunina M, Kravtsov Alexander, Sysoev I, Blinov Andrey. Synthesis and study of thin TiO₂ films doped with silver nanoparticles for the antireflection coatings and transparent contacts of photovoltaic converters. *Semiconductors.* 2016;50: 1231-1235. DOI: 10.1134/S1063782616090141.
- Kravtsov Alexander, Chikulina Irina, Tarala Vitaly, Vakalov Dmitry, Nikova Marina, Malyavin F, et al. Nucleation and growth of YAG: Yb crystallites: A step towards the dispersity control. *Ceramics International.* 2020;46. DOI: 10.1016/j.ceramint.2020.08.016
- Siddiqui Shahida A, Andrey V Blinov, Alexander V Serov, Alexey A Gvozdenko, Alexander A Kravtsov, Andrey A Nagdalian, et al. Effect of Selenium Nanoparticles on Germination of Hordéum Vulgäre Barley Seeds Coatings. 2021; 11(7):862. Available:https://doi.org/10.3390/coatings11070862
- Siddiqui SA, Ahmad A, Siddiqui AA, Chaturvedi P. Stability Analysis of a Cantilever Structure using ANSYS and MATLAB, 2021 2nd International

- Conference on Intelligent Engineering and Management (ICIEM). 2021;7-12.
DOI: 10.1109/ICIEM51511.2021.9445357
19. Blinov AV, Gvozdenko AA, Kravtsov AA, Krandievsky SO, Blinova AA, Maglakelidze DG, et al. Synthesis of nanosized manganese methahydroxide stabilized by cysteine. *Materials Chemistry and Physics*. 2021; 2651:124510.

© 2021 Muzayeva et al.; This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Peer-review history:

The peer review history for this paper can be accessed here:
<https://www.sdiarticle5.com/review-history/78712>